

Production of Mg–3Al Based Composites Reinforced with Ti6Al4V Particles

L.C. KUMRUOGLU*

University of Cumhuriyet, Engineering Faculty, Metallurgy and Materials Department, Sivas, Turkey

Stir casting is one of the simple, flexible and the cost effective methods for fabricating of metal matrix composites reinforced with particles. In this study, 5%, 10%, 15 vol.% Ti6Al4V particles were added into the Mg–3Al melt during stirring. The tensile strength of Mg–3Al alloy was between 150–190 MPa and 5 vol.% Ti6Al4V/Mg–3Al alloy was equal. However, increasing the particle volume of Ti6Al4V powders to 10 vol.% and 15 vol.% decreased the ultimate tensile strength of composites to 140–170 MPa and 90–110 MPa, respectively. On the other hand, the hardness of reinforced composite was increased for each volume.

DOI: [10.12693/APhysPolA.125.432](https://doi.org/10.12693/APhysPolA.125.432)

PACS: 83.80.Ab, 81.05.Bx, 81.05.Ni, 81.70.–q

1. Introduction

Magnesium is the lightest of all the structural metallic materials and is primarily used in engineering alloys due to its low density, fatigue resistance, high strength-to-density ratio, machining ability and castability [1, 2]. Pure magnesium is not appropriately robust to be used in many engineering applications. Magnesium matrix composites occupy various advantages over monolithic Mg alloys, for example high specific strength and stiffness, high elastic modulus, good creep, and wear resistances [3]. Furthermore, particle reinforced Mg composites produced by stir casting are very economic, capable of several applications in the aerospace, defense, and automobile industries [3]. However, the relatively low corrosion and wear resistance of magnesium alloys restricted their widespread use [4]. So as to develop the mechanical properties of Mg alloys, research efforts have been focused on the development of metal matrix composites. Mg can be reinforced with hard ceramic particles. Conversely, it may reduce the ductility and toughness. In comparison with ceramic particles, metallic particles mostly have a much better wettability with liquid metals [5], better ductility and mechanical compatibility through the metallic matrix can be potentially employed as a reinforcement component in metal matrix composites [6]. Considering the low density, high strength and more biocompatibility, the Ti and its alloys are the promising candidates for the reinforcement materials. Ti6Al4V alloy is not only lighter, but also has three times higher yield and tensile strength than pure Ti [5]. Finally, the nodular particles made from Ti6Al4V alloy have been added to the Mg–3Al alloy.

This article presents an attempt onto production of Mg–3Al (matrix)–Ti6Al4V (reinforcement) composite via stir casting route. The stir casting process was also

verified and optimized by computer simulation. Eventually, the final microstructure and mechanical properties such as yield-ultimate tensile strength, elongation, and microhardness have been investigated.

2. Experimental studies

Conventional gravity casting is still the most widely used method of casting magnesium alloys. That is why gravity casting method was preferred to produce pre-alloy. The Mg–3Al (97% Mg, 3% Al) alloy was melted in a graphite crucible with the induction heater protected by CO₂–2%SF₆. The volumes of Ti6Al4V particles in ratio of 0%, 5%, 10% and 15 vol.% were prepared by vortex method injecting the particles into the Mg–3Al melt while the melt was stirred. A Microtrac Flex particle size analyzer characterized Ti6Al4V particles. The average size of Ti6Al4V particles was 280 μm (diameter) (Fig. 1) and the shape of particles was sphere. The stirring was continued for 15 min to produce homogeneous mixture. The speed of impeller was 250 rpm.

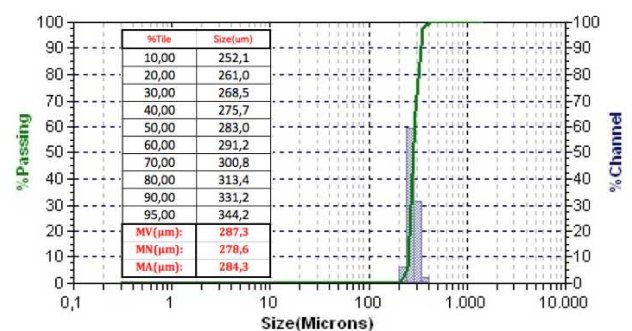


Fig. 1. Average diameter and ratio of Ti6AL4V particles.

The stirring continued to prepare the homogeneous slurry. After stirring, the composite slurry was poured into the graphite mold. The pouring temperature was selected as 750 °C. The temperature of composite slurry

*e-mail: leventcenk@gmail.com

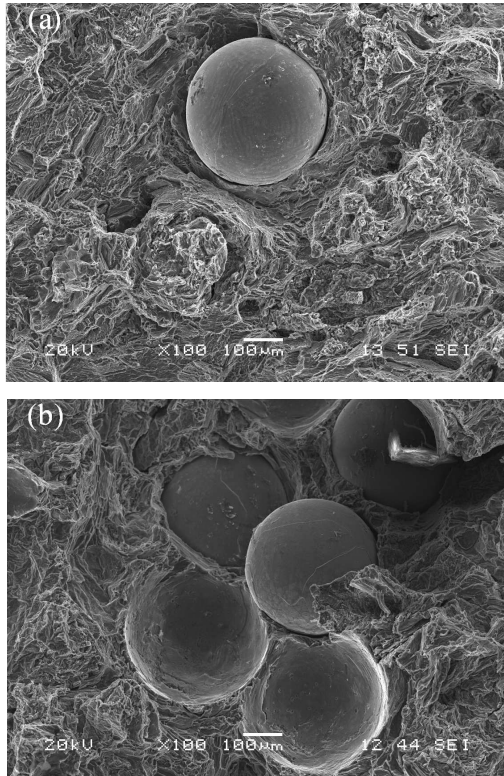


Fig. 6. SEM view of fractured surfaces of (a) 5% Ti6Al4V and (b) 15% Ti6Al4V specimens.

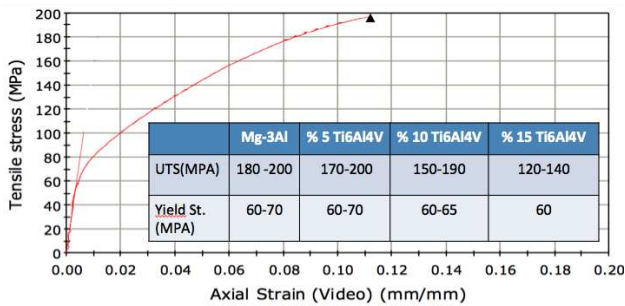


Fig. 7. Tensile test graph of 5% Ti6Al4V specimen and the table of tensile test reports of all specimens.

Tensile test results were given in Fig. 7. It can be concluded that tensile strength of 15% reinforced specimen is the lowest value, but 5% and 10% are closer to the Mg-3Al mechanical properties. On the other hand, the yield strength of composite is also closer to the Mg-3Al. On the other hand, the hardest one was 15% Ti6Al4V specimen (90 HBN-hardness Brinell).

4. Conclusions

Ti6Al4V particle reinforced Mg-3Al alloy based metal matrix composites were successfully produced by using vortex method and gravity casting technique. The results obtained from the microstructure investigations reveal that the homogeneous particle distributions in the composites were obtained. The addition of Ti6Al4V particles increased the density of the composites and hardness. HBN increased linearly with increasing particles volume fraction. The highest values were obtained from the 15% Ti6Al4V-Mg-3Al composite. Tensile strength decreased with increasing the particle volume fraction.

References

- [1] A.A. Luo, M.O. Pekguleryuz, *J. Mater. Sci.* **29**, 5259 (1994).
- [2] K.U. Kainer, *Magnesium Alloys and Technology*, Wiley-VCH, Weinheim 2003.
- [3] X.J. Wang, X. Hu, K. Wu, M. Zheng, Q. Zhai, *J. Mater. Sci.* **44**, 2759 (2009).
- [4] X.J. Li, X.Y. Liu, B.L. Luan, *Appl. Surf. Sci.* **257**, 9135 (2011).
- [5] H.Z. Ye, X.Y. Liu, *J. Alloys Comp.* **402**, 162 (2005).
- [6] C.K. Seal, K. Vince, M.A. Hodgson, *Mater. Sci. Eng. A* **4**, 012011 (2009).