

Proceedings of the 11th Polish–Japanese Joint Seminar on Micro and Nano Analysis, Gniez, September 11–14, 2016

Modification of Microstructure and Properties of Extruded Mg–Li–Al Alloys of α and $\alpha + \beta$ Phase Composition using ECAP Processing

J. DUTKIEWICZ^{a,*}, S. RUSZ^b, W. MAZIARZ^a, W. SKUZA^a, D. KUC^c AND O. HILSER^b

^aInstitute of Metallurgy and Materials Science, Polish Academy of Sciences,

W.S. Reymonta 25, 30-059 Kraków, Poland

^bTechnical University Ostrava, Department of Mechanical Engineering, 17 Listopadu 15, Ostrava, Czech Republic

^cSilesian Technical University, Department of Metallurgy and Materials Science,

Z. Krasińskiego 8, 40-019 Katowice, Poland

Two magnesium based alloys containing 4.5 wt% Li and 1.5 wt% Al (alloy 1) and 9 wt% Li and 1.5 wt% Al (alloy 2) were cast under argon atmosphere and hot extruded at 350 °C. Microstructure of alloy 1 consisted of hexagonal α phase of average grain size 20 μm and small aluminum rich precipitates being the most probably AlLi_2Mg phase. Alloy 2 in the extruded form consisted of lamellas of $\alpha + \beta$ phases of thickness 5–20 μm and length above 100 μm . Significant grain refinement down to about 2 μm was observed in one-phase hexagonal (hcp) alloy 1 after one pass of ECAP processing with helical component. Two-phase (hcp + bcc) alloy 2 showed higher non-homogeneity after the first equal channel angular pressing pass due to easier deformation of softer bcc phase, while both, α and β phases exhibited low angle grain boundaries. The hardness and the yield strength of the alloys were higher for alloy 1 (68 HV and 205 MPa, respectively) than those of alloy 2 (61 HV and 175 MPa). Subsequent equal channel angular pressing passes were performed at lower extrusion stress. The hardness of both alloys did not change significantly after subsequent equal channel angular pressing passes and revealed tendency to decrease. Two-phase alloy showed superplastic properties already after one equal channel angular pressing pass at 160 °C with grain growth after superplastic tensile testing. Single phase hcp alloy did not show such properties after 1 pass, but after a few equal channel angular pressing passes it could be superplastically formed.

DOI: [10.12693/APhysPolA.131.1303](https://doi.org/10.12693/APhysPolA.131.1303)

PACS/topics: 83.50.-v, 81.40.Lm, 81.20.Fw

1. Introduction

Mg–Li alloys are the lightest structural materials with a high specific strength and stiffness, good magnetic screening, and shock resistance ability. Precipitates and solute atoms are expected to be the main obstacles for dislocation motion at lower temperatures in hexagonal α type alloys. Cross slip causing stress drop with increasing temperature is presumably the dominant thermally activated mechanism at higher temperatures [1]. The addition of aluminum and copper to the α or β type Mg–Li alloys brings about the significant improvement of the age hardening effect in the α phase, although a limited data concerning the structure of precipitates was given [2, 3]. The magnesium–8 wt% lithium alloy was reported in [4] to consist of hcp (α) and bcc (β) phases, with the α phase appearing as plates in the β matrix. A near Burgers orientation relationship was observed between the two phases, i.e., $[0001]_\alpha \parallel [0-11]_\beta$, and $(-100)_\alpha \parallel (-211)_\beta$. Two-phase Mg–Li–Al alloy processed by conventional extrusion followed by equal channel angular pressing (ECAP) at room temperature (RT) showed that the grains of the β phase matrix were sub-

stantially refined, with the mean size decreasing from 60 μm to 200 nm [4, 5]. Additionally, the α precipitates, embedded in the β grains and the ternary MgLiAl_2 phase coexisting with the α precipitates were homogenized by ECAP processing. The significant grain refinement was reported in the cast Mg–8 wt% Li alloy after ECAP at the temperature of 473 K [6]. Following extrusion and subsequent two passes of ECAP led to excellent superplastic properties, including the maximum elongation of $\approx 970\%$ at 473 K at the strain rate of $1.0 \times 10^{-4} \text{ s}^{-1}$. The strain rate sensitivities under the optimum superplastic conditions were measured as $m \approx 0.4-0.6$. The superplastic forming was also reported in ultrafinegrained Mg–9Li–1Zn (LZ91) alloy sheets prepared through high-speed-ratio differential speed rolling (HRDSR) [7] giving in consequence the grains of α and β phases reduced to the size of $\approx 1 \mu\text{m}$. The HRDSRed alloy exhibited the enhanced strength and ductility at room temperature and excellent low temperature superplasticity in the temperature range 423–523 K. The Mg–Li alloy with 8 wt% Li was processed by high-pressure torsion (HPT) to achieve ultrafine grains with the average grain size of 500 nm. The alloy showed good superplastic properties at the strain rate of 10^{-3} s^{-1} starting at the temperature of 50 °C or higher [8].

In the present paper the ECAP method combined with helical part in horizontal area of the channel was applied

*corresponding author; e-mail:

to increase the extrusion force applied in order to decrease the grain size of α and $\alpha + \beta$ grains. The changes of microstructure and mechanical properties were examined in alloys of either α or $\alpha + \beta$ phase composition. A small aluminum addition was applied to MgLi alloys in order to increase their mechanical properties and to study its effect on superplasticity in the single and two-phase alloys.

2. Experimental procedure

Two magnesium based alloys of compositions 4.5 wt% Li and 1.5 wt% Al (alloy 1) intended to contain the α phase (hcp) and 9 wt% Li, 1.5 wt% Al (alloy 2) intended to be composed of $\alpha + \beta$ (hcp + bcc) phases were cast under argon atmosphere and extruded at 350 °C to obtain bars of cross-section 12 × 12 mm² suitable for the ECAP deformation. The ECAP tool consisted of helical part in the horizontal area of the channel with the angle of lead $\gamma = 30^\circ$. The basic aim of the use of helix consisted in the simulation of back pressure and thus in the increase of extrusion force. Up to 3 ECAP passes were applied using rotation of samples in the subsequent passes. The extrusion force was measured during the process. The hardness of samples was tested using a Zwick ZHU 250 instrument in the Vickers method and the tensile tests were performed applying an Instron 6025 testing machine at room and elevated temperatures using samples of thickness 2 mm and width 3.5 mm, testing length 18 mm and total length 45 mm cut out after ECAP by an electro-spark machine. The structure and composition were studied using a Philips CM20 or FEI Technai G6 transmission electron microscopes and Leica DM IRM optical microscope. Thin samples of hot pressed or ECAPed alloys were cut by electro spark device, then electropolished in electrolyte consisting of 750 ml AR grade methanol, 150 ml butoxyethanol, 16.74 g magnesium perchlorate and 7.95 g lithium chloride and finally dimpled using Gatan dimpler and ion beam thinned using Leica EM RES101 ion beam thinner. The X-ray diffraction was performed using a Philips PW 1710 diffractometer with Co K_α radiation.

3. Results and discussion

Figure 1 shows optical microstructures of extruded alloys 1 and 2 in the as extruded condition. One can see that the alloy 1 consists mostly of equiaxial hexagonal α grains of the average size of 60 μm . Based on X-ray diffraction, only hexagonal α grains were identified, although darker particles could be also seen, which the most probably resulted from the aluminum addition in the form of AlLi or Mg₁₇Al₁₂ phases as suggested in [1]. The formation of MgLi₂Al particles was also suggested to appear at higher Li content [9]. The microstructure of alloy 2 consisted of two types of elongated grains of the α phase (bright color) and the β phase (gray color), which were identified using X-ray diffraction as hexagonal α and bcc β phase.

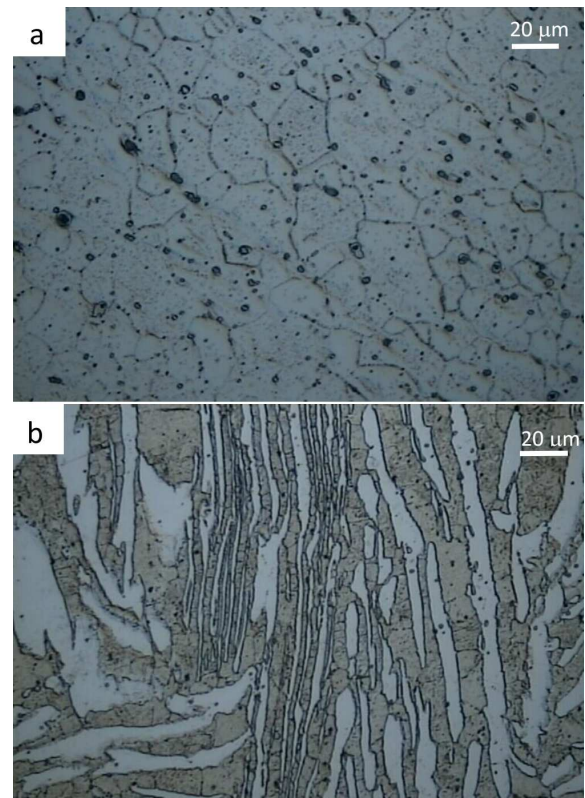


Fig. 1. Optical microstructures of as hot extruded at 350 °C alloys 1 (a) and 2 (b).

It is obvious that the cellular dendritic-like α phase is uniformly dispersed within the β phase matrix. The similar structure was observed in the two phase $\alpha + \beta$ alloy reported in [4, 6]. Figure 2 shows the results of hardness measurements of the investigated alloys 1 and 2 in the as extruded state and after 1–3 ECAP passes processed at 250 °C and 160 °C, respectively. One can see that in alloy 1 hardness decreases from 70 HV to 60 HV after the first pass, then slightly raises to 62 HV and then decreases again, while in alloy 2 it decreases gradually from 61 to 60 after the first pass, then to 58 HV after the second one and then stabilizes. In another work on two-phase MgLiZn alloys, a slight increase of hardness was observed after HRDSR [7], however it might have been due to different deformation treatment leading to lower hardness (50 HV). In the single phase hexagonal MgLi alloys hardening was reported to result from precipitates and work.

Figure 3 shows a photograph of samples after ECAP processing, in which their helical shape can be seen. The graph shows extrusion strain versus ECAP displacement during 1–3 passes. One can see that the flow stress at 250 °C decreases with the following passes from about 130 MPa for the first pass down to 100 MPa after the third pass. It indicates most probably an increasing participation of grain boundary sliding with the subsequent passes.

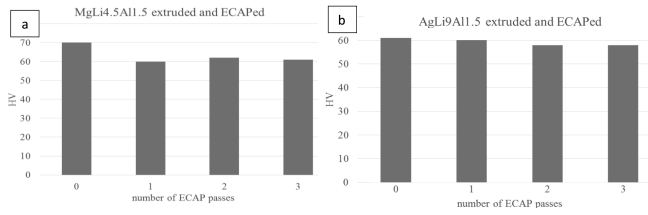


Fig. 2. Graphs showing (a) results of HV₁₀ hardness measurements of alloy 1 (MgLi_{4.5}Al_{1.5}) after 0–3 ECAP passes at 250 °C and (b) results of HV₁₀ hardness measurements of alloy 2 (MgLi₉Al_{1.5}) after 0–3 ECAP passes at 160 °C.

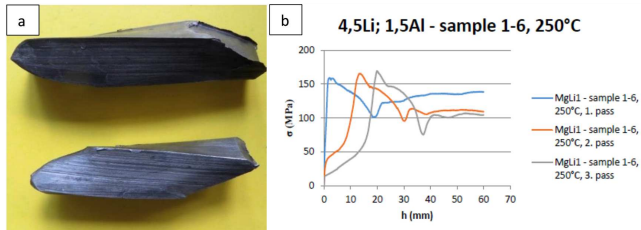


Fig. 3. (a) Samples of alloy 1 after 1 and 3 ECAP passes and (b) stress versus sample ECAP displacement relationship during 1–3 passes of extruded alloy during ECAP processing at 250 °C.

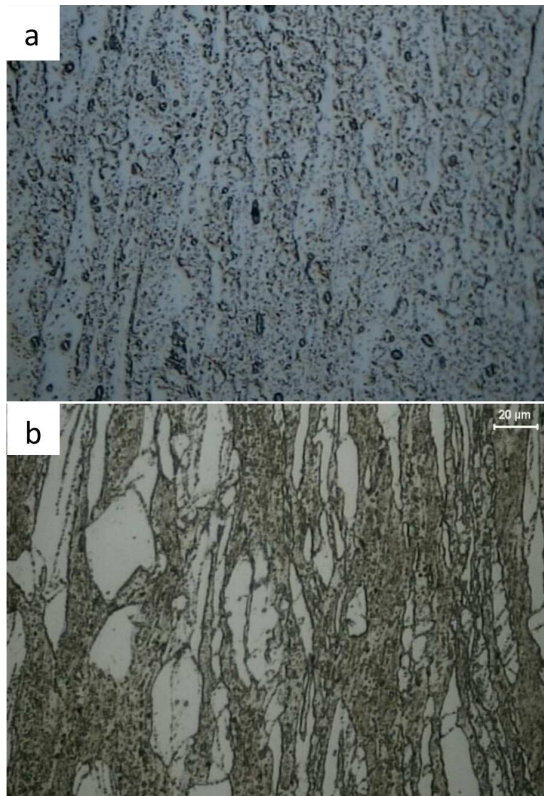


Fig. 4. Optical microstructures of as hot extruded at 350° alloys 1 and 2 after 1 pass of ECAP processing at temperature of 250 °C (alloy 1, (a)) and at 160 °C (alloy 2, (b)) showing grain elongation toward the ECAP pressing direction.

The optical microstructures after the first ECAP pass show a significant directionality of elongated and refined grains (Fig. 4a and b). In both alloys some nonhomogeneity of deformation can be seen, however it is larger in alloy 2. It seems that it is caused by lower strength of the bcc Li rich phase, which more easily undergoes deformation [6–10].

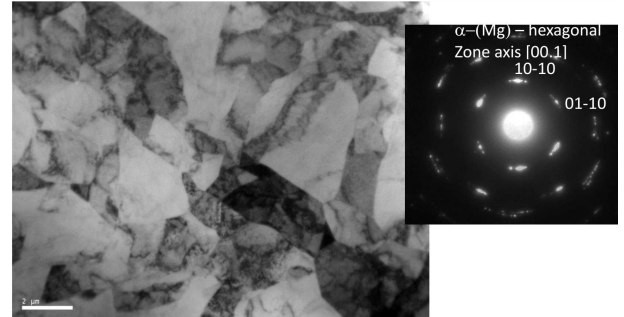


Fig. 5. TEM micrograph of alloy 1 after one pass of ECAP processing at 220 °C. Grain refinement with mostly low angle grain boundaries as results from the diffraction pattern reflections diffused along Debye-Scherrer rings (inset) can be observed.

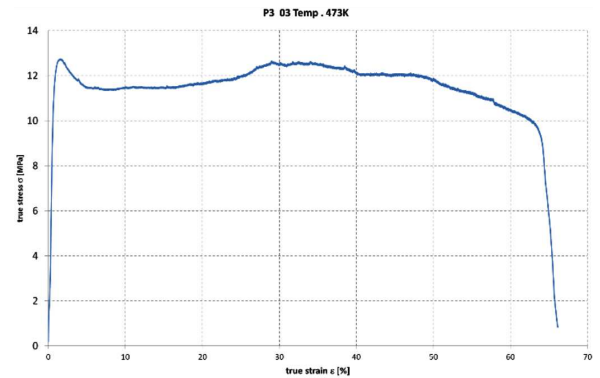


Fig. 6. Tensile test performed at 200 °C at rate 10^{-4} s^{-1} using sample cut from alloy 2 after 1 ECAP pass at 160 °C. One can see deformation at low, almost constant stress of 12 MPa and elongation approaching 70%, indicating superplastic deformation.

TEM microstructure of alloy 1 after the first pass is shown at a relatively low magnification; softening is connected with cross slip and the dislocation climb process [10] which may be a reason for small deformation hardening (Fig. 5). It can be seen that fine grains of the average size near $2 \mu\text{m}$ do not contain directionality, which was typical for the initial grains. The diffraction pattern from the visible area shows basically the same orientation of zone axis [0001].

The reflections from the hexagonal α phase are diffused along the Debye-Scherrer rings indicating a low angle misorientation between subgrains formed during the first pass of ECAP processing. The tensile test performed

at rate 10^{-4} s^{-1} and the same temperature of 160°C like ECAP was performed, showed a high elongation near 70% which was lower than that observed for other superplastic two phase MgLi alloys [6, 7, 10]. However, the sample after HPT carried out at lower temperature showed significantly better superplastic properties after ECAP than the other alloys [10]. On the other hand, the method has limitations concerning the size of samples and inhomogeneity of deformation. The single phase hexagonal alloy 1 after an ECAP pass at 220°C showed elongation only slightly better than that of ECAP processed at room temperature. Moreover, a higher number of ECAP passes was needed to induce superplasticity, which was easily attainable in two phase alloys after only 1 ECAP pass, as shown in Fig. 6.

4. Conclusions

- One pass of ECAP deformation with a helical component led to significant grain refinement down to about $2 \mu\text{m}$ in hexagonal (hcp) single phase and two (hcp = bcc) phase alloys. Two phase alloy 2 showed higher non-homogeneity due to easier deformation of softer bcc phase, while both alloys exhibited low angle grain boundaries after ECAP. Subsequent ECAP passes could be performed at lower extrusion stresses. The hardness of both alloys did not change significantly after ECAP passes and revealed tendency to decrease.
- Two phase alloy showed superplastic properties already after one ECAP pass at 160°C showing grain growth after superplastic tensile testing. Single phase (hcp) alloy did not show such properties after 1 pass, but after a few ECAP passes it could be superplastically formed.

Acknowledgments

The financial support of the OPUS research project No. 2014/15/B/ST8/03184 is gratefully acknowledged.

References

- [1] Z. Drozd, Z. Trojanová, S. Kúdela, *J. Alloys Comp.* **378**, 192 (2004).
- [2] G.H. Park, J.T. Kim, H.J. Park, Y.S. Kim, H.J. Jeong, N. Lee, Y. Seo, J.Y. Suh, H.T. Son, W.M. Wang, J.M. Park, K.B. Kim, *J. Alloys Comp.* **680**, 116 (2016).
- [3] N. Saito, M. Mabuchi, M. Nakanishi, K. Kubota, K. Higashi, *Scr. Mater.* **36**, 551 (1997).
- [4] M.V. Kral, B.C. Muddle, J.F. Nie, *Mater. Sci. Eng. A* **460-461**, 227 (2007).
- [5] T. Liu, S.D. Wu, S.X. Li, P.J. Li, *Mater. Sci. Eng. A* **460-461**, 499 (2007).
- [6] M. Furui, Ch. Xu, T. Aida, M. Inoue, H. Anada, T.G. Langdon, *Mater. Sci. Eng. A* **410-411**, 439 (2005).
- [7] W.J. Kim, M.J. Kim, J.Y. Wang, *Mater. Sci. Eng. A* **516**, 17 (2009).
- [8] H. Matsunoshita, K. Edalati, M. Furui, Z. Horita, *Mater. Sci. Eng. A* **640**, 443 (2015).
- [9] J. Zhang, Yang Zhang, G. Wu, W. Liu, L. Zhang, W. Ding, *Mater. Sci. Eng. A* **621**, 198 (2015).
- [10] Z. Trojanova, Z. Drozd, P. Lukac, F. Chmelik, *Mater. Sci. Eng. A* **410-411**, 148 (2005).