

Proceedings of the European Conference "Physics of Magnetism 96", Poznań 1996

STRUCTURAL AND MAGNETIC PROPERTIES OF $\text{Dy}(\text{Fe}, \text{V}, \text{Si})_{12}$ COMPOUNDS

Z. DRZAZGA, A. WINIARSKA, A. CHROBAK

Institute of Physics, University of Silesia
Uniwersytecka 4, 40-007 Katowice, Poland

AND D. KACZOROWSKI

Institute of Low Temperature and Structure Research
Polish Academy of Sciences
P.O. Box 937, Wrocław 2, Poland

An influence of Si on the structural and magnetic properties of $\text{Dy}(\text{Fe}, \text{V}, \text{Si})_{12}$ compounds is studied. X-ray diffraction shows that these materials crystallise in the tetragonal ThMn_{12} -type structure. An increase in the saturation magnetization, the Curie temperatures and magnetocrystalline anisotropy in the Si substitutional systems is observed when compared with $\text{DyFe}_{12-x}\text{V}_x$. The magnetic properties depend on the preferential site occupation and concentration of Si and V atoms in these compounds.

PACS numbers: 61.10.-i, 75.30.Cr, 75.30.Gw, 75.50.Gg

1. Introduction

Iron-rich intermetallic compounds of the ThMn_{12} -type structure have been proposed as inexpensive alternatives for permanent magnetic materials. It is known that the rare earths and iron do not form the binary RFe_{12} phase, a third element is necessary to stabilize the tetragonal ThMn_{12} -type structure [1]. These compounds have the composition $\text{RFe}_{12-x}\text{M}_x$, in which M represents a nonmagnetic 3d element, for instance Ti, V, Cu or metalloid Si. Apart from the R elements and 3d elements, which mainly determine the magnetic properties of the compounds, also stabilizing elements contribute to the magnetic properties. The aim of this work is to study the influence of the substitution of Si instead of V on the magnetic properties of $\text{DyFe}_{12-x}\text{M}_x$ compounds.

2. Experimental

Samples of nominal composition $\text{DyFe}_{10}\text{V}_{2-x}\text{Si}_x$, $\text{DyFe}_9\text{V}_{3-x}\text{Si}_x$ and $\text{DyFe}_8\text{V}_{4-x}\text{Si}_x$ ($x = 0.05, 1.0, 1.5, 2.0$) were prepared by arc-melting. The samples were prepared in the same way as those described in [2].

The structure and homogeneity of these compounds were checked by X-ray diffraction and thermomagnetic measurements. Lattice parameters were measured

using X-ray powder diffractometer Siemens 5000 with Cu K_α radiation. Recorded lines were fitted with X-Profilr (written by A. Kachel) and the IIX61 programme was applied to find exact values of the lattice parameters.

Magnetic moment was studied at fields up to 5 T in the temperature range 1.7 K to room temperature. Magnetocrystalline anisotropy was investigated by means of ac susceptibility and torsion measurements in the temperature range 77–293 K. The easy direction of magnetization (EMD) was determined from X-ray diffraction of aligned powders. The most of the samples showed the easy c -axis at room temperature. Thermomagnetic curves at high temperatures were measured using a Faraday balance.

3. Results and discussion

All investigated compounds have the tetragonal ThMn_{12} -type structure. Slight decrease in the a and the c parameters with the increase in Si content were observed but the Vegard law was not fulfilled (Fig. 1).

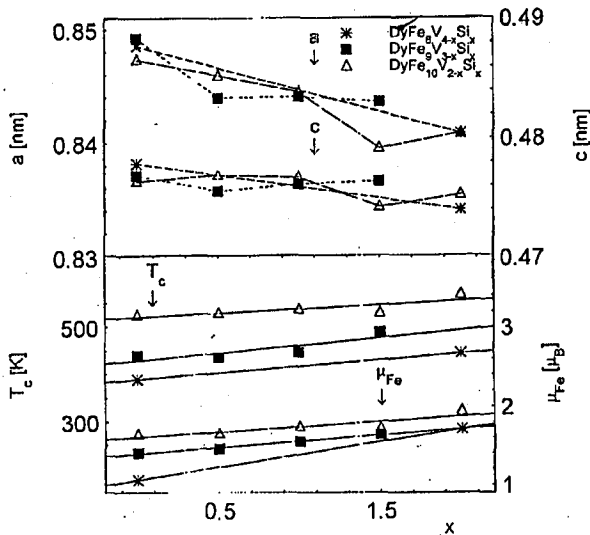


Fig. 1. Lattice parameters, T_c and average $\mu(\text{Fe})$ for $\text{DyFe}_{12-x}(\text{V},\text{Si})_x$ versus Si concentration.

The investigated compounds are ferrimagnets with the Curie temperatures above room temperature. Plot of T_c as a function of silicon concentration is presented in Fig. 1. The values of T_c are almost unchanged for $\text{DyFe}_{10}\text{V}_2\text{Si}_x$ but increase in silicon-rich compounds of $\text{DyFe}_9\text{V}_3\text{Si}_x$ and $\text{DyFe}_8\text{V}_4\text{Si}_x$. The Curie temperature for $\text{DyFe}_8\text{V}_2\text{Si}_2$ is about 60 K higher than for DyFe_8V_4 . Moreover, as shown in Fig. 2, the resultant magnetization increases with the Si content. Assuming that the magnetic moment of the Dy ions takes its free-ion value ($10\mu_B$) the magnetic moment of the Fe atoms can be calculated from the values of the saturation magnetization obtained at 1.7 K. The estimated moment on Fe atom increases

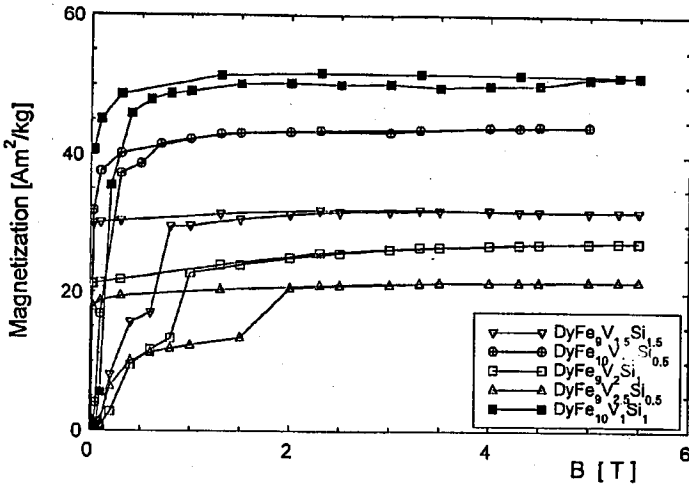


Fig. 2. Magnetic isotherms obtained at 1.7 K.

markedly in $\text{DyFe}_{12-x}(\text{V},\text{Si})_x$ systems when compared with $\text{DyFe}_{12-x}\text{V}_x$. This is attributed to the enhancement of the exchange interaction due to the replacement of V by Si atoms. The effect of substituted Si atoms is similar to that observed in $\text{DyFe}_{12-x}(\text{V},\text{C})_x$ under carbon doping [2].

The ac-initial magnetic susceptibility versus temperature curves of $\text{DyFe}_{10}\text{V}_{2-x}\text{Si}_x$ (Fig. 3) shows strong anomalies which are shifted towards higher temperatures with increase in x . These peaks of ac-susceptibility correspond to spin reorientation due to magnetocrystalline anisotropy competition between the 3d and rare-earth sublattices. At room temperature the EMD is determined by the Fe sublattice but at low temperatures the negative Dy anisotropy contributions cause the spin reorientation transition. The torsion measurements confirm the tilting of the EMD from the c -axis with lowering temperature. A cone ordering of the magnetic moments is observed for all studied compositions at 77 K. Generally, silicon content increases temperature of the beginning of the spin reorientation transition. The anisotropy constants reported for $\text{YFe}_{10}\text{V}_2$ and $\text{YFe}_{10}\text{Si}_2$ are nearly the same [3]. It follows that magnetocrystalline anisotropy of dysprosium sublattice is enhanced because any essential changes in the 3d sublattices are not expected.

The analysis of spin reorientation in compounds with lower concentration of iron (e.g. $\text{DyFe}_9\text{V}_{3-x}\text{Si}_x$ and $\text{DyFe}_8\text{V}_2\text{Si}_2$) is more complicated. It should be noticed that metamagnetic behavior of resultant magnetic moment is observed at low temperatures (Fig. 2). Changes in the magnetization under the action of an external field seem to indicate the spin-flip. It follows from Fig. 2 that the critical field values depend on vanadium and silicon content in $\text{DyFe}_{12-x}(\text{V},\text{Si})_x$ series. The results of torsion measurements also demonstrate an influence of the applied magnetic field on the magnetic arrangement in the studied compounds.

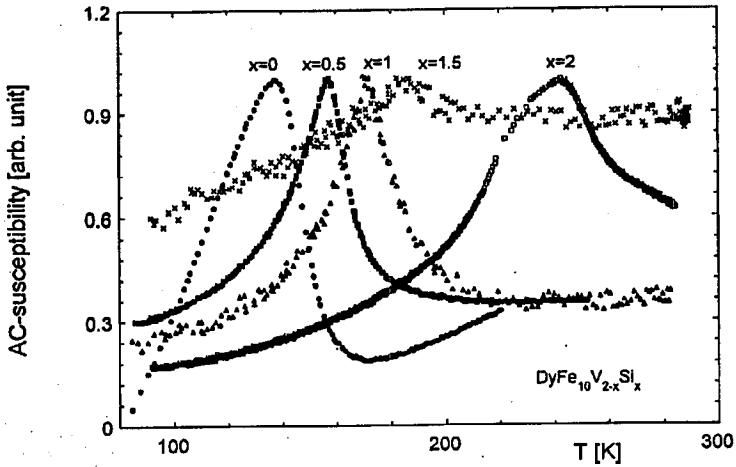


Fig. 3. ac-initial magnetic susceptibilities for series $\text{DyFe}_{10}\text{V}_{2-x}\text{Si}_x$.

The EMD in $\text{DyFe}_9\text{V}_{3-x}\text{Si}_x$ determined from torsion curves at 77 K in sufficiently small magnetic field is still the c -axis but markedly tilts from the c -axis in magnetic fields higher than 0.4 T. Temperature and field dependence of the spin reorientation transition are due to the varying the nonmagnetic M element concentration.

The obtained results indicate that magnetic properties of $\text{DyFe}_{12-x}\text{M}_x$ depend on the stabilizing element M. In these compounds, three different crystallographic sites are available for the Fe and M atoms. The V atoms prefer the 8i sites [3] whereas the Si atoms share the 8j and 8f positions with the Fe atoms [4]. The deeper analysis taking into account the various distribution of the Fe and M atoms and its influence on the exchange and crystal field interactions responsible for magnetic behavior in the studied compounds will be done elsewhere.

Acknowledgments

Authors are indebted to Professor R. Troć for making possible the measurements of magnetization at 1.7 K. This work is partly supported by grant No. 2 P30224403.

References

- [1] W. Suski, in: *Handbook on the Physics and Chemistry of Rare Earths*, Vol. 22, Eds. K.A. Gschneidner, Jr., L. Eyring, Elsevier, Amsterdam 1996, Ch. 149, p. 143.
- [2] Z. Drzazga, A. Winiarska, W. Zarek, E. Popiel, L. Gladczuk, *J. Alloys Comp.* **230**, 76 (1995).
- [3] M. Solzi, L. Pareti, O. Moze, W.I. Dawid, *J. Appl. Phys.* **64**, 5084 (1988).
- [4] C. Christides, M. Anagnostou, Hong-Shuo Li, A. Kostikas, D. Niarchos, *Phys. Rev. B* **44**, 2182 (1991).